

Avery Dennison®


Tips for Applying Protective Overlay

Instructional Bulletin : # 8.64
Revision : # 03
Last Updated : April 2019

This bulletin provides recommendations for the application of Avery Dennison OL-100o, OL-2000 and OL-4000 clear protective overlay films. Please follow the proper operating and safety procedures recommended by the laminator manufacturer.

Contents

- Laminating Equipment
- Laminator Set-Up Tools
 - Nip Impression Paper
- General Guidance
 - Lamination using a Graphics Finishing Laminator with Roll to Roll Capability
 - Lamination of Sheeted Prints using a Graphics Finishing Laminator
 - Lamination of Sheeted Prints using a Manual Squeeze Roll Laminator
- Laminating Gap Adjustment
- Application Startup
- Troubleshooting

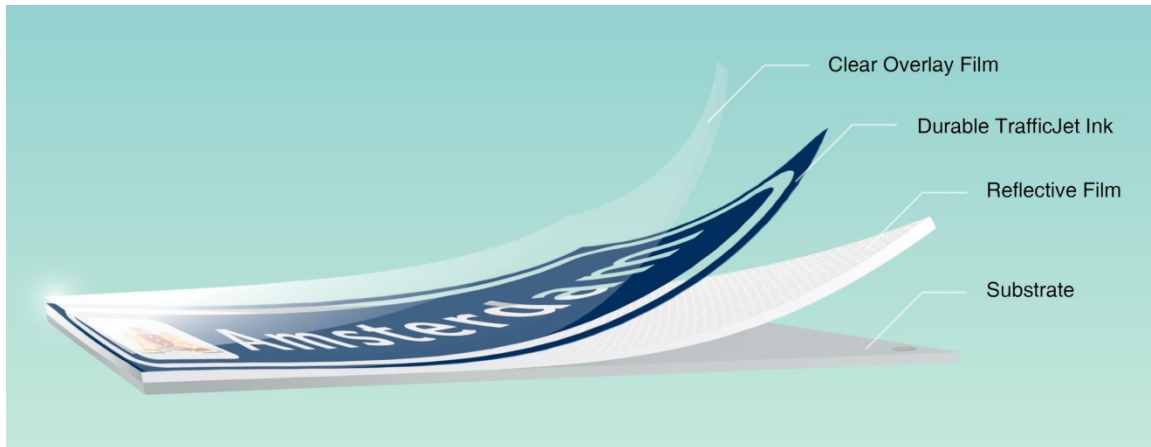

Important

It is important that the printed media is fully cured and dried prior to laminating. Laminating a print before it is fully cured and dried can cause signs to fail (adhesion failures, separation of the laminate from the media, etc.) and void the sign performance warranty.

In certain areas, the minimum recommended drying time is 12 hrs for OL-2000, 2 hrs for OL-1000, 2hrs for OL-4000 of free exposure to air between the printing and laminating process.

For best drying results, lay the prints flat and exposed to air (not stacked) or unroll and release tension in the printed roll to create air space over the face of the sheeting in the roll. Allow the roll to stand vertically and preferably elevated on a grid to allow for improved airflow and evaporation of the ink solvent.

Laminating Equipment

To properly apply Avery Dennison protective overlay films, a laminator is recommended. The information contained in this bulletin applies to the use of Avery Dennison OL-1000, OL-2000 and OL-4000 clear films with the proper equipment.

For specific information regarding equipment, follow the manufacturer's instructions or consult with the manufacturer's technical service department.

Laminator Set-Up Tools

In addition to the setup procedures and tools recommended by the laminator manufacturer, it is recommended that the nip pressure and footprint of the laminator be monitored.

Nip Impression Paper

Nip impression paper is a wax transfer paper used to determine the evenness of the nip footprint across the width of the laminating rolls. If the footprint is inconsistent (too heavy on the edges, too heavy in the middle, or too heavy on one side), poor toner transfer, poor toner bond, or wrinkles may result. Nip impression paper can be obtained from this source:

Beloit Manhattan Division

P. O. Box 155, Ivy Park
Clarks Summit, PA 18411
Phone: (717) 587-5111

Recommended Product

"Nip Impression Kit for Covered Rolls"

General Guidance

The following general recommendations apply to laminating Avery Dennison printed films with Avery Dennison OL-1000, OL-2000 and OL-4000 clear overlay films. For specific instructions relating to equipment operation, please refer to the instructions provided by the laminator manufacturer.

Important!

The use of heat is not required when laminating Avery Dennison OL-1000 or OL-2000 clear overlay films onto material printed with the Trafficjet Print System.

Heat cannot be used to laminate OL-4000 and should have almost break-free tension to avoid edge lifting.

Sheeting type	OL-1000	OL-2000	OL-4000
T-1500D	Yes	Yes	No
T-2000	Yes	Yes	No
T-6000	Yes	Yes	No
W-6000*	No	No	Yes*
T-7000	Yes	Yes	No
T-9000	Yes	Yes	No
T-11000	Yes	Yes	No

*Temporary signs printed with Black and Red inks for 3 year warranties.

Instructional Bulletin IB# 8.64

Tips for Applying Overlay

Page 2 of 5

reflectives.averydennison.com



Reflective
Solutions

Requirements

OL films	Heat	Pressure (psi)	Speed (m/min)
OL-1000	No	50-70	
OL-2000	No	50-70	
OL-4000	No	50-70	0-2.5

Lamination using a Graphics Finishing Laminator with Roll to Roll Capability

To laminate printed Avery Dennison films roll to roll, mount the printed film on the bottom roll unwind and follow laminator manufacturer recommendations for unwinding from the bottom shaft. Pull the printed film through the front nip (image side up). Continue pulling the web evenly through the back pull rolls. Close the back pull roll nip and apply 50PSI (350kPa).

Mount the Avery Dennison OL-1000/OL-2000/OL-4000 clear overlay film on the top unwind and web according to the laminator manufacturer recommendations. Pull the release liner away from the overlay film and adhesive. Attach the liner to the upper rewind shaft to accumulate the delaminated liner. Pull the overlay film and adhesive evenly through the front nip until the web is wrinkle free with even tension across the web. Close the front nip and adjust the pressure to 50PSI (350kPa). Start running the laminator at 1.0FPM (0.3 m/min). Cut away the overlaminated film and adhesive before it reaches the back nip.

As the laminated film passes through the back roll nip, inspect the web for signs of wrinkling, waviness, bubbles, etc. If problems are evident, stop and correct them before proceeding. Once the laminated film looks good, increase the speed to 4 FPM (1.2 m/min.).

Lamination of Sheeted Prints using a Graphics Finishing Laminator

To hand feed printed sheets into the laminator, web the Avery Dennison OL-1000/OL-2000/OL-4000 overlay as instructed in this section. Use a length of release liner beneath the print to protect the bottom roll from contacting the adhesive. The liner can also be used as a leader to begin sheet feeding.

Once the Avery Dennison Overlay Film has passed through the front nip, close the front nip and adjust the pressure to 50 PSI (350 kPa). Start running the laminator at a speed of 1.0 FPM (0.3 m/min). Cut away the non laminated clear film between front and back nips.

When the Avery Dennison Overlay Film is feeding evenly, begin feeding printed sheets into the nip, taking care to align the sheets evenly with the overlay. Increase the running speed as desired. Adjust the overlay unwind brake to maintain the minimum tension required to keep the overlay free from wrinkles. As the sheets exit the back pull roll nip, cut between the sheets.

Lamination of Sheeted Prints using a Manual Squeeze Roll Laminator

These applications are driven by a hand crank and can be run by one or more operators. They are intended for the individual application of signs.

Laminating Gap Adjustment

This procedure may vary from application to application depending on such factors as flatness and material thickness. When common materials are being used, keep a record of the optimum settings to duplicate during future runs.

1. Raise the top roller to create a gap larger than the thickness of the printed sheeting.
2. Place the printed sheeting between the opened laminating rollers.
3. Slowly lower the top roller until it evenly touches the substrate from edge to edge. Continue to lower the roller one half turn to obtain adequate pressure.

Application Startup

1. With the overlay face down, peel back one to two inches of the release liner, folding it to expose the adhesive.
2. Turn the sheeting over and carefully align the sign face with the substrate. Press the exposed adhesive side down slowly onto the substrate. Work from the center towards the outer edges.
3. Feed the adhered section into the squeeze roller up to the folded portion of the release liner.
4. Drape the remaining sheeting over the top roll and peel back the remaining portion of the release liner, while feeding in the remainder of the sign blank.
5. Carefully trim all excess material downward at an angle with a sharp utility blade. Make sure to not chip or damage the reflective sheeting.

Troubleshooting

Problem	Possible Cause	Solution
Wrinkles in film going into nip	Tension too low	Increasing unwind brake setting on affected web
	Uneven feeding of web	Cut web and rethread according to steps described
	Uneven tension across web	Reduce unwind brake setting momentarily and then increase to bring tension back up
Mottle or air bubbles in laminated graphic ("silvering")	Not enough pressure at nip	Increase pressure. See corresponding section of this document
	Running too fast	Reduce speed in 0.5 FPM (0.15 m/min.) increments
	Uneven footprint in nip	Check graphic if mottle has consistent repeat in roll direction or is heavier on one side, problem may be in laminator setup or laminator rolls. Refer to instruction manual or contact laminator manufacturer
Mottle in adhesive coat		Check pattern if it is consistent across web or decreases in repeat as roll unwinds, problem may be adhesive related. Try slower speed or higher pressure.

The above Avery Dennison literature provides information to the user for proper application, storage and other requirements. Please refer to Product Data Bulletins or your local Avery Dennison Representative for warranty information. Find the latest information on the Avery Dennison website, www.reflectives.averydennison.com. We encourage you to check our website periodically for updates.

All statements, technical information and recommendations about Avery Dennison products are based upon tests and information believed to be reliable, but do not constitute a guarantee or warranty of any kind. All Avery Dennison products are sold with the understanding that Purchaser has independently determined the suitability of such products for its intended and other purposes.

For technical questions, please contact:

North America: reflective.tech.na@averydennison.com

Europe, Middle East & Africa: reflective.tech.eu@eu.averydennison.com

Asia Pacific: reflective.tech.ap@ap.averydennison.com

South America: reflective.tech.sa@averydennison.com